

AD-A065 364

CORNELL UNIV ITHACA NY DEPT OF ELECTRICAL ENGINEERING F/G 20/12
INVESTIGATION OF ADVANCED TECHNOLOGY AND HIGH FIELD ELECTRONIC --ETC(U)
JAN 79 L F EASTMAN, C E WOOD DAAG29-77-G-0066

UNCLASSIFIED

ARO-13405.4-EL

NL

1 OF 1
ADA
065364



END
DATE
FILMED

4 -79
DDC

LEVEL II

AR8 13405.4-EL ⑤

INVESTIGATION OF ADVANCED TECHNOLOGY AND HIGH
FIELD ELECTRONIC PROPERTIES OF InP FOR MICROWAVE DEVICES

FINAL REPORT

Covering the Period
November 15, 197~~6~~⁵ - November 14, 1978

by


Lester F. Eastman and Colin E. C. Wood

for

U.S. Army Research Office
P.O. Box 12211
Research Triangle Park, N.C. 27709

Contract No. DAAG29-77-G-007⁶⁶₆

76 G 0082

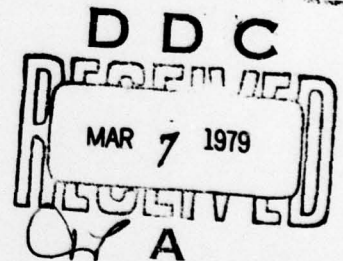

CORNELL UNIVERSITY
Dept. of Electrical Engineering, Phillips Hall
Ithaca, N.Y. 14853

APPROVED FOR PUBLIC RELEASE;
DISTRIBUTION UNLIMITED

See 1473

79 02 26 005

AD A0 65364

DDC FILE COPY

INVESTIGATION OF ADVANCED TECHNOLOGY AND HIGH FIELD
ELECTRONIC PROPERTIES OF InP FOR MICROWAVE DEVICES

Final Progress Report on Contract No. DAAG29-77-G-0076;

76 G 0082


Progress in the understanding of preparation and properties of InP material has been made in the following main areas.

First in the area of liquid phase epitaxial growth a breakthrough has been made in the understanding of parameters required for the preparation of high purity material.

By secondary ion mass spectrometry the single most important residual donor impurity in layers was found to be silicon.¹ The silicon is present from two sources and has been reported to have a segregation coefficient ~ 30 .² First, source indium as supplied contains silicon which can be reduced by baking in a hydrogen ambient containing a few ppm of H_2O vapor according to



Second, there is a dynamic production of volatile SiO which contaminates the melt from the walls of the growth tube, according to



Calculations of the thermodynamics of these systems showed that the silicon content could be reduced by baking at lower and lower temperatures, however, at $680^\circ C$ the kinetics of Si_{In} removal becomes too slow for practical interest ($\sim 4-5$ days).³ It was

79 02 26 005

predicted, however, that H_2O vapor introduced into the growth tube during bakeout will reduce the Si much faster, a procedure that was successfully used by S. Groves of Lincoln Labs to obtain high purity ($\mu_{77} \sim 60,000 \text{ cm}^2/\text{Vsec}$) epilayers after an overnight bakeout. (Reported at St. Louis GaAs Conference 1978).⁴

The state-of-the-art L.P.E. InP is now held at Cornell with $(N_D - N_A) \sim 4 \times 10^{14} \text{ cm}^{-3}$ with 77K mobilities as high as $94,000 \text{ cm}^2 \text{ V}^{-1} \text{ sec}^{-1}$. It is now possible to produce material of this quality on a semi routine basis. Several films have been supplied to external laboratories for further characterization, notably Oxford University (Prof. Stradling's group) for photoconductivity analysis and to Wright Patterson Air Force Base for photoluminescence studies.

An instability effect has been found for these high purity films. After a shelf life of several months or heating at $\sim 100^\circ\text{C}$ for several days, the 77K mobility was found to rise to as high as $140,000 \text{ cm}^2/\text{Vsec}$ and the donor density to drop anomalously. In certain cases the resistivity became too high to allow measurement of electrical properties. This effect, since confirmed on Cornell material at Lincoln Labs, was not, however, found with back doped films (using Sn dopant) and appears only with residual $(N_D - N_A)$ initially below 1×10^{15} . We feel that this effect is possibly due to silicon site exchange or to intrinsic point defects. We are currently endeavoring to relate this effect to the presence of certain deep levels found by optical D.L.T.S. (see below).

Material produced in this program was subsequently used for

Be⁺ ion implantation in cooperation with J. Comas of Naval Research Labs to produce shallow P⁺ n junction which could be used for studies of the breakdown properties of InP. Subsequent study of implant profiles by S.I.M.s at Cornell before and after annealing at 625°C for 15 minutes showed it was possible to produce ideal profiles and hence good abrupt junctions when the implant dose was below $3 \times 10^{13} \text{ cm}^{-2}$, however, much above this figure ($6 \times 10^{13} \text{ cm}^{-2}$) anomalous diffusion occurred on annealing making junctions graded.⁵

With the $3 \times 10^{13} \text{ cm}^{-2}$ implanted films, good $1/C^2$ Vs V characteristics were found enabling impurity profiles to be obtained and breakdown voltages of the order 40% higher than the equivalently doped GaAs were found. This effect subsequently has been confirmed by workers at Varian Associates⁶ and the University of Southern California.⁷

The diodes produced in this implantation study were also used for optically stimulated deep level transient capacitance spectroscopy (ODLTS) using a YAG laser. No electron traps were found in concentrations above the detection limit ($\sim 2 \times 10^{12} \text{ cm}^{-3}$), however, two hole traps were found with ionization energies $\sim 0.1 \text{ eV}$ and 0.5 eV believed similar to those observed in L.P.E. GaAs. The concentrations of these traps were respectively $> 6 \times 10^{13} \text{ cm}^{-3}$ and $\sim 4 \times 10^{12} \text{ cm}^{-3}$.

References

- 1) InP with $N_D - N_A = 4 \times 10^{14}/\text{cc}$ and $\mu_{77} = 24\text{K cm}^2\text{V}^{-1}\text{sec}^{-1}$, Ip, K.T., Ph.D. Thesis (1978), Cornell University.
- 2) Baumann, G.G., Benz, K.W. and Pilkuhn, H.H., Segregation coefficient of Si = 30, J. Electrochem. Soc., 123, 1232, (1978).
- 3) Wrick, V.L., Ip, K.T. and Eastman, L.F., J. Electronic Mat., 7, 253, (1978).
- 4) Groves, S.H. and Planko, M.C. "Growth of Undoped InP and $\text{In}_{(1-x)}\text{Ga}_x\text{As}_y\text{P}_{(1-y)}$ by LPE", GaAs and Related Compounds Conf., St. Louis, Missouri, Sept. 1978, Inst. of Phys. Conf. Series No. 45, Chap. 2.
- 5) Devlin, W.J., Ip, K.T., Leta, D.P., Eastman, L.F., Morrison, G.H. and Comas, J., "PN junction Formation in n-InP by Be Ion Implantation", GaAs and Related Compounds Conf., St. Louis, Missouri, Sept. 1978, Inst. of Phys. Conf. Series No. 45, Chap. 8.
- 6) Berenz, J. (Varian Associates), private communication (1978).
- 7) Kao, C.W. and Crowell, C.R., Workshop on Hot Electron Phenomena in Semiconductors, Cornell University, August 17-19, 1978. (proceedings unpublished).

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

18

AR 13405.4-EL

REPORT DOCUMENTATION PAGE

READ INSTRUCTIONS
BEFORE COMPLETING FORM

1. REPORT NUMBER

2. GOVT ACCESSION NO.

3. RECIPIENT'S CATALOG NUMBER

4. TITLE (and Subtitle)

Investigation of Advanced Technology and
High Field Electronic Properties of InP
for Microwave Devices,

5. TYPE OF REPORT & PERIOD COVERED

Final Report
11/15/78- 11/14/78

6. PERFORMING ORG. REPORT NUMBER

7. AUTHOR(s)

Lester F./Eastman Colin E.C./Wood

8. CONTRACT OR GRANT NUMBER(s)

DAAG29-77-G-0076,

DAAG29-76-G-0082

9. PERFORMING ORGANIZATION NAME AND ADDRESS

Cornell University
Dept. of Electrical Engineering
Ithaca, N.Y. 14853

11. CONTROLLING OFFICE NAME AND ADDRESS

U.S. Army Research Office
P.O. Box 12211
Research Triangle Park, NC 27709

12. REPORT DATE

January 1979

13. NUMBER OF PAGES

4

14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)

15. SECURITY CLASS. (of this report)

Unclassified

15a. DECLASSIFICATION/DOWNGRADING
SCHEDULE

16. DISTRIBUTION STATEMENT (of this Report)

Approved for public release; distribution unlimited.

(9) Final rept. 15 Nov 75-14 Nov 78.

17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)

N/A

18. SUPPLEMENTARY NOTES

The findings in this report are not to be construed as an
official Department of the Army position, unless so designated by
other authorized documents.

19. KEY WORDS (Continue on reverse side if necessary and identify by block number)

20. ABSTRACT (Continue on reverse side if necessary and identify by block number)

Silicon has been identified as the most important single donor in InP grown by Liquid Phase Epitaxy. The conditions for minimizing this impurity have been defined. State-of-the-art purity by L.P.E. is now held at Cornell with $\mu_{77} = 94,000 \text{ cm}^2/\text{V.s}$ and $N_D - N_A \sim 4 \times 10^{14} \text{ cm}^{-3}$.

Be ion implantation has allowed good shallow p^+n junctions to be prepared which have subsequently been used to profile donor

DD FORM
1 JAN 73

1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

411091

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

concentration through epitaxial layers, to determine that the bulk breakdown fields in InP are ~40% higher than in equivalently doped GaAs and to find (for the first time) two hole traps by optical transient capacitance spectroscopy. (~0.1 eV and ~0.5 eV) above the valence band.

ACCESSION for	
NTIS	White Section <input checked="" type="checkbox"/>
DDC	Buff Section <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION _____	
BY _____	
DISTRIBUTION/AVAILABILITY CODES	
Dist. AVAIL. and/or S. C. C. N. L.	
A	

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)